

Biosynthesis and Characterization of Silver Nanoparticles using Single Garlic Callus Extract (*Allium sativum* L.)

Yanti Puspita Sari^a, Amanda Qory Suchi^a, Rudy Agung Nugroho^{b*}

^aDepartment of Biology, Faculty of Mathematics and Natural Sciences, Mulawarman University, Jl. Barong Tongkok No. 4 Gn. Kelua, Samarinda, East Kalimantan 75123, Indonesia; ^bAnimal Physiology, Development, and Molecular Laboratory, Department of Biology, Faculty of Mathematics and Natural Sciences, Mulawarman University, Jl. Barong Tongkok, Gunung Kelua Campus, Samarinda, East Kalimantan 75123, Indonesia

Abstract Nanotechnology is a relatively new and innovative field with huge potential for application in the food and drug industries. Due to their excellent physicochemical and biological properties, silver nanoparticles (AgNPs) are often utilized in various applications and have been the subject of substantial research. AgNP synthesis using plant extracts has recently gained popularity due to their environmental friendliness, affordability, and potent functionality in several applications. The present study evaluated the biosynthesis, stability, and characteristics of AgNPs using a single garlic callus extract (*Allium sativum* L.) AgNPs were synthesized using single garlic callus extract (AgNPs-As) by adding 1 mM AgNO₃ to ethanolic extracts of single garlic callus at a 1:9 ratio, incubating at 35 °C for 48 h, and observing the colloidal color change. Spectrophotometry (absorption at 200–800 nm), SEM, EDX, PSA, FTIR, and XRD were used for their characterization. The present study showed a colloidal color change to brown, indicating the formation of AgNPs-As. The characterization of AgNPs-As using SEM, EDX, PSA, and XRD revealed a spherical morphology with an average size of 201.9 nm. Several active compounds were identified from different peaks, indicating the presence of several types of biological functional groups, such as alkaloids, terpenoids, carbonyl groups, esters, halides, and alcohol were also confirmed using FTIR spectroscopy.

Keywords: Silver nanoparticle, biosynthesis, stability, garlic, callus.

Introduction

Nanotechnology is the field of science that deals with the synthesis, engineering, and manipulation of matter. Materials that have a size of less than 100 nm are classified as nanoparticles [1]. The application of nanoparticles is growing rapidly in various disciplines because of the novel properties and increased activity related to their size, distribution, and morphology, and they are widely used in health, energy, environment, and several industrial fields [2]. Research has been conducted on nanoparticles from various types of metals including titanium [3], gold [4], and silver [5].

Titanium dioxide nanoparticles (TiO₂ NPs) are among the most commonly manufactured and used NPs in the world [6]. However, various in vitro and in vivo investigations have shown the negative impacts of TiO₂ NPs in biological systems and documented the genotoxic, carcinogenic, and photosensitization behavior of these particles (SCCS/1516/13) [7, 8]. Meanwhile, recent work by Kim *et al.* [9] employing an embryonic zebrafish model to investigate the impact of the surface charge and size of gold nanoparticles (AuNPs) on in vivo toxicity has demonstrated that surface functionalization correlated with toxicity results in developing organisms [14]. In addition, the body weight of the mice injected with gold nanoparticles fluctuated temporarily but returned to normal after 10–14 days [10].

*For correspondence:

rudyagung.nugroho@fmipa.unmul.ac.id

Received: 23 March 2023

Accepted: 27 July 2023

©Copyright Sari. This article is distributed under the terms of the [Creative Commons Attribution License](#), which permits unrestricted use and redistribution provided that the original author and source are credited.

Further, silver nanoparticles (AgNPs) are among the most effective and efficient metal nanoparticles as electronic components and antibacterial [11, 12], antidiabetic [13], antifungal, antiviral [14], anticancer [15], anti-inflammatory compounds [16, 17], and are used in various industrial fields because they are safe for human health [18]. The synthesis of AgNPs can be carried out by various methods, namely physical, chemical, and biological methods. The biosynthesis of AgNPs using plant extracts is an alternative method for the manufacture of AgNPs. Though unidentified processes may influence the process of synthesizing AgNPs using plant extracts [19-21], green synthesis of AgNPs using plant extracts is environmentally friendly, economical, and easy to perform on an industrial scale without the need for large amounts of energy and hazardous chemicals [22].

The plant extract used in the biosynthesis of AgNPs acts as a reductant capable of reducing silver salts (Ag^+) to metallic silver (Ag^0). The phytochemicals present in plant extracts also act as capping agents for nanoparticles, providing the advantages of preventing the agglomeration of nanoparticles, reducing toxicity, and increasing antimicrobial activity [23]. One of the plants with a high phytochemical content is *Allium sativum* [24] and a single garlic plant (*Allium sativum* L.), which contains organosulfur, the main bioactive compounds (including alliin, allicin, allyl sulfide, ajoene, and dithiane) [25], and phenolic compounds that act as antioxidants [26].

The production and harvesting of secondary metabolites from plants *in vivo* require a long time, and limited land availability is a consideration for the production of secondary metabolites through tissue culture techniques on an industrial scale. Cell biomass is produced in large quantities and in a short time by stimulating cells through cell growth media [27]. According to Nurchayati *et al.*, [28], the crumb callus structure can be used in the production of secondary metabolites by cell suspension culture.

Previous studies successfully used the callus extract of *Cinnamomum camphora* [18], *Solanum incanum* [29], and *Celastrus paniculatus* [30] as bioreductors for AgNPs biosynthesis. Moreover, Hasanin *et al.*, [31] studied the biosynthesis of zinc and selenium oxide nanoparticles, which have potential antimicrobial properties against Gram-negative and -positive bacteria, in combination using the callus extract of *Ziziphus spina-christi*.

Tissue culture to produce callus involves growing cells, organs, tissues, or the entire plant *in vitro* under aseptic and regulated environmental and nutritional conditions [32]. Plant tissue culture techniques have recently been used as an important tool for large-scale plant propagation, disease management, and the improvement of plant secondary metabolite synthesis. In a continuing process, a small portion of the tissue (explant) is employed to reproduce plants [33]. The use of plant tissue culture avoids exposing the plant to biotic and abiotic stressors that impact secondary metabolite synthesis [34]. Furthermore, the advantages of using callus for the biosynthesis of AgNPs include obtaining a higher yield value at a low cost, reducing the use of plants in nature in high quantities, and preventing contamination; additionally, the callus acts as a source of phytochemicals that can be propagated in the laboratory [35].

Although various studies regarding the use of plant extracts and callus for AgNP biosynthesis have been performed, the biosynthesis of AgNPs using a single garlic callus (AgNPs-As) has not been done thus far. Therefore, the present study aimed to biosynthesize AgNPs-As using various concentrations of AgNO_3 and evaluate their characteristics using scanning electron microscopy (SEM), energy dispersive X-ray (EDX), particle size analyzer (PSA), Fourier-transform infrared spectroscopy (FTIR), and X-ray diffraction (XRD).

Materials and Methods

Sterilization and Callus Induction

All chemicals (analytical grade) used in the present study were obtained from Sigma Aldrich, Inc. USA. Single-clove garlic was collected from Bandung, West Java, Indonesia. The fresh garlic was sterilized using sterile water, fungicides (0.2%), and bactericides (0.2%) for 20 min followed by Clorox (10%) for 1 min and then rinsed with distilled water. Thereafter, garlic embryos were inoculated in Murashige and Skoog supplemented with 90 g.L^{-1} sucrose and 5 ppm picloram. After the callus cells had formed, the callus was sub-cultured in fresh medium after 3 weeks.

Preparation of Ethanolic Callus Extract

The callus was macerated in 95% ethanol (1:2 callus:ethanol) for 48 h until the maceration solution was clear; then, the extract mixture was filtered using Whatman paper no. 2. After filtration, the filtrate was concentrated using a rotary evaporator (Buchi, Switzerland) at a temperature of 50–55 °C to eliminate

the solvent. Then, 2 g of the thick extract was weighed, dissolved in 20 mL of deionized water, and used for the biosynthesis of nanoparticles [36].

Biosynthesis of AgNPs-As

The biosynthesis of AgNPs-As was carried out using 1 mM of AgNO₃ as a precursor. AgNPs-As biosynthesis was performed by mixing 1 mL of single garlic callus extract with 9 mL of 1 mM AgNO₃ solution (1:9) and incubating at 35 °C for 48 h, followed by observation for color change.

Characterization of AgNPs-As

The nanoparticle colloid was centrifuged at 10,000 rpm for 15 min and then dried using a freeze dryer (Alpha 1-2 LO, Germany). The AgNPs were characterized using UV-visible spectroscopy (UV-VIS; SP-UN52N, Beijing, China), SEM (SU 3500, Hitachi, Europe), FTIR (Alpha II, Bruker, USA), PSA (SZ-100, Horiba, Kyoto, Japan), and XRD (Bruker D8, Blue Scientific, USA).

Results and Discussion

Significant global interest has been shown in the development of a biologically inspired green synthesis of silver nanoparticles for use in medical research and the treatment of diseases. The AgNPs-As developed in this study have potential uses in diagnostics, biomarkers, cell labeling, antimicrobial agents, drug delivery, and cancer treatment. Furthermore, the AgNPs-As may also contribute to water treatment and the creation of environmentally friendly nanofertilizers, nanopesticides, and nanoherbicides.

Color Change and UV-VIS Analysis of AgNPs-As

The combination of a 10% solution of yellow garlic callus ethanol extract and a clear solution of 1mM AgNO₃ solution resulted in a color change from light yellow to brown (Figure 1), indicating the biosynthesis of AgNPs-As. Such a color change was previously observed by Botcha and Prattipati [37] in the aqueous extract of *Hyptis suaveolens* callus, which changed from light yellow to dark brown. The color change during the formation of AgNPs-As is mediated through the reduction of Ag⁺ to Ag⁰ by a reducing agent contained in the extract. Furthermore, phenolic compounds in the extract may play a role in the reduction of Ag⁺ to Ag⁰, while the presence of protein promotes the stability of AgNPs [37]. Other important phytochemical compounds for Ag⁺ reduction include terpenoids, flavonoids, ketones, aldehydes, amides, and alkanolic acids [38]. Usmani *et al.* [39] and Patil *et al.* [40] have reported that the inclusion of phytochemicals, such as flavonoids, alkaloids, glycosides, terpenoids, phenols, carbohydrates, proteins, enzymes, and coenzymes, contributes to the green synthesis of AgNPs as bioreductors and stabilizing agents (Figure 2).

The secondary metabolites in the callus extract that function as reducing, stabilizing, and capping agents during the formation of AgNPs-As caused the reaction mixture to change color as they converted silver ions (Ag⁺) into elemental silver (Ag⁰) [41, 42]. In addition, differences in the color formed depend on the compound contained in the callus extract [43].

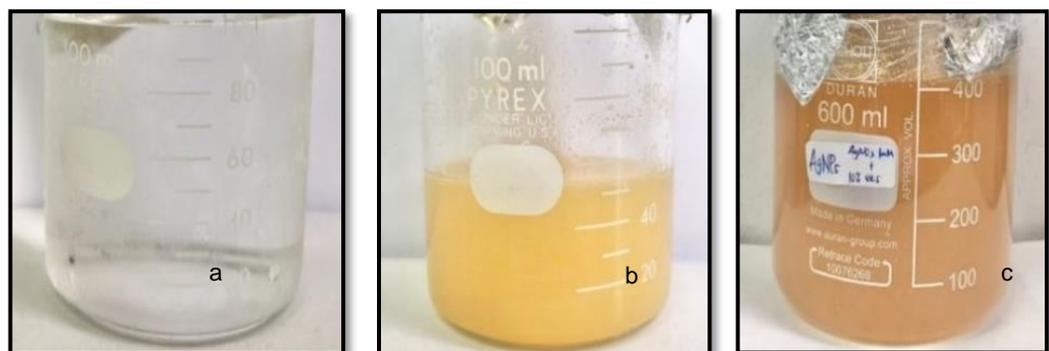


Figure 1. Color change during the biosynthesis of AgNPs-As. a) AgNO₃ solution; b) Garlic callus ethanol extract; c) Resulting AgNP-As after 24 h

Furthermore, the wavelengths of the AgNPs-As colloidal suspension were examined between 200 and 800 nm, with the typical UV absorption spectra being found at 400 nm (Figure 3). The color shift of the solution caused by Surface plasmon resonance (SPR) stimulation during the green synthesis of AgNP-As has been shown in several previous studies [44-46]. Along with the obvious color shift, a peak was also observed in the UV-VIS absorption spectra around 400 nm in this study in accordance with previous work [47].

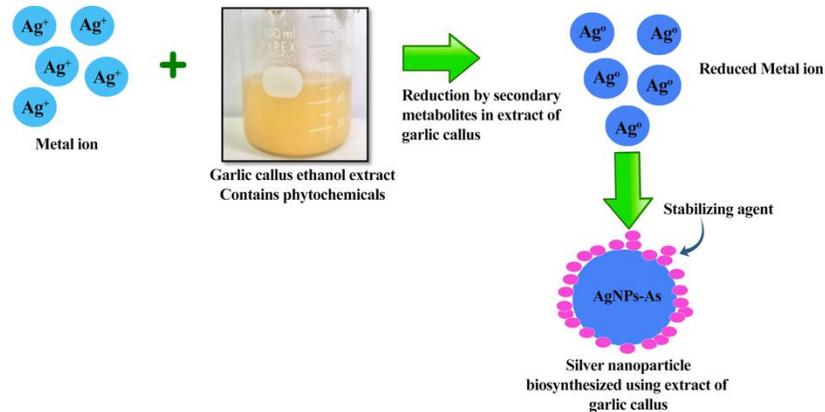


Figure 2. Reduction of silver using single garlic callus extract to produce silver nanoparticle

Characterization of AgNPs-As

The SEM of the AgNPs-As revealed that particles were evenly distributed and spherical in shape (Figure 4). The results of the characterization using SEM with EDX analysis revealed strong signals from C and K (49.57%), O and K (6.15%), Cl and K (10.07%), and Ag (34.21%; Figure 5). Because of their SPR, these AgNPs-As exhibited a strong peak at 3 keV, confirming the existence of silver ions as well as other elements, carbon, oxygen, and chlorine, as reducing and capping agents (Figure 6). The lack of nitrogen guaranteed the full reduction of AgNO₃ to silver ions, and no additional trace ions were found in the nanoparticles (Table 1).

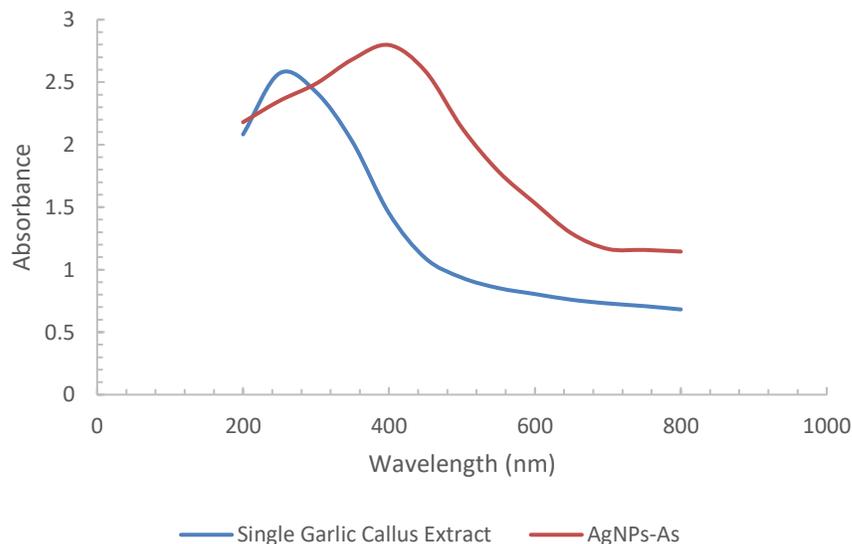


Figure 3. UV-VIS spectra of the biosynthesis of AgNPs using the ethanolic extract of single garlic callus and 1 mM of AgNO₃ (AgNPs-As)

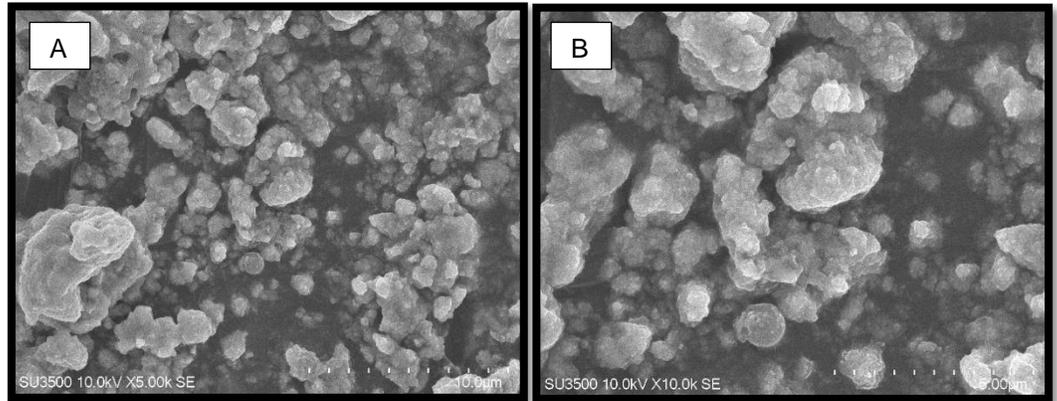


Figure 4. Scanning electron micrographs of AgNPs synthesized from single garlic callus (*Allium sativum*). a) Mag 5.000; b) Mag 10.000

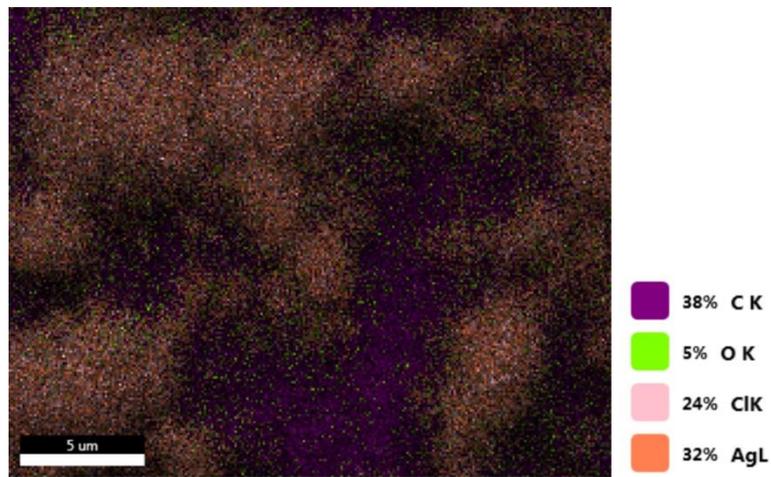


Figure 5. The EDX element overlay map of AgNPs-As synthesized using single garlic callus extract

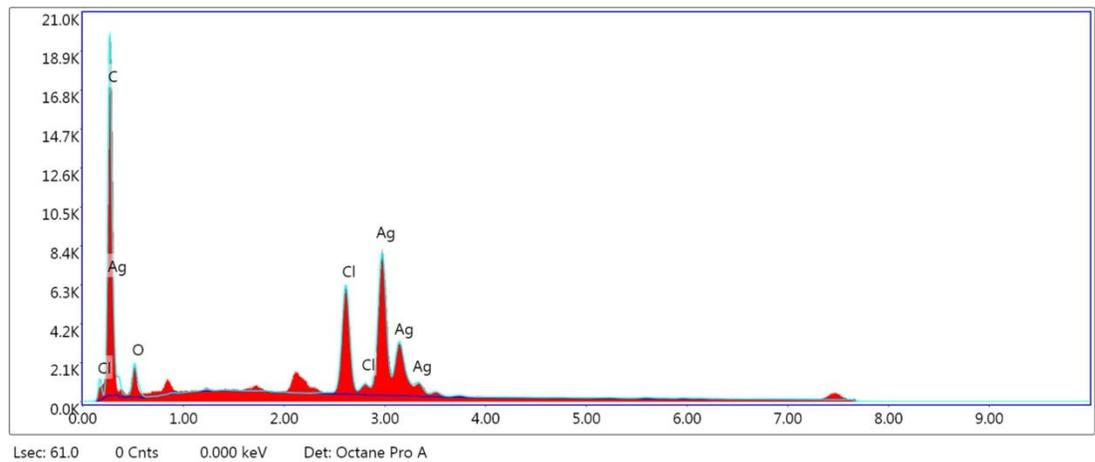
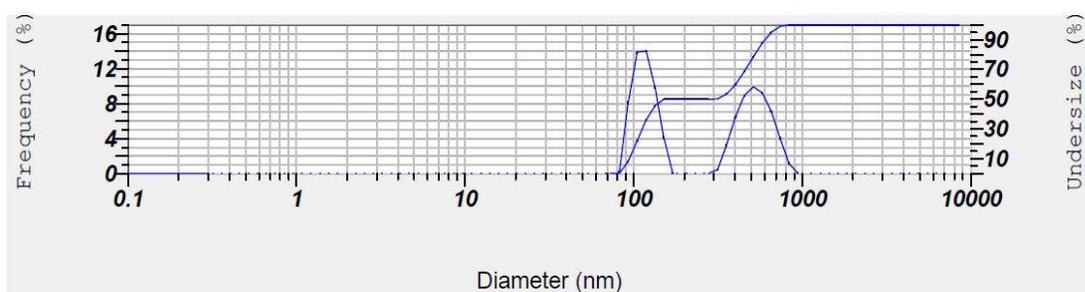


Figure 6. The EDX spectrum of AgNP-As depicts an Ag peak between 2 and 3 keV

Table 1. The EDX spectrum analysis of AgNPs synthesized using single garlic callus extract

Element	Weight (%)	Atomic (%)	Net. Int.
C K	49.57	80.73	2866.60
O K	6.15	7.51	276.20
Cl K	10.07	5.56	1833.60
AgL	34.21	6.20	2635.10

The AgNPs-As size was analyzed using a PSA, revealing an average size of 201.9 nm (Figure 7). In comparison to using *Allium cepa* (onion) extract as a bioreductor agent to produce silver nanoparticles, Naseer *et al.* [48] have shown that the resulting silver nanoparticles had an average size of 84.8 nm, ranged in size from 30–100 nm, and were spherical. Further, the biosynthesis of AgNPs using callus extracts of *Hyptis suaveolens* [37], *Solanum incanum* L [29], and *Taxus yunnanensis* [35] produced AgNPs with a spherical shape. The particle size is strongly influenced by the concentration of plant extracts containing phenols, polyphenols, polysaccharides, anthocyanins, and tannins, which play a role in the reduction of Ag⁺ in the formation of stable nanoparticles [49]. Particles with a diameter of 100–2500 nm are referred to as fine nanoparticles [50].

**Figure 7.** Particles size distribution of AgNPs synthesized using single garlic callus extract

The FTIR spectrum recorded from 4000 to 600 cm⁻¹ revealed different peaks indicating the presence of several types of biological functional groups that may play a pivotal role in reduction and stabilization during the biosynthesis of AgNPs-As. The results of the FTIR test on the ethanolic extract of single garlic callus (Figure 8a) revealed absorption peaks (%) of 3265.86, 2926.98, 1634.81, 1514.69, 1407.93, 1348.99, 1264.13, 1032.32, and 923.33. The high-intensity peak 3265.86 belonged to an O-H bond, which is an alcohol compound with hydrogen or phenol bonds. Meanwhile, the medium absorption peak 2926.98 corresponded to a C-C bond, which is an alkane compound. At the absorption peaks 1634.81 and 1514.69 belonging to a C=C bond were alkenes and benzene compounds. The intensity peaks 1407.93 and 1348.99 belonged to a C-H bond, which is an alkane compound. The peak at 1264.13 belonged to a C-N bond, which is an amine or amide compound. Meanwhile, the weak absorption peaks 1032.32 and 923.33 belonged to a C-O bond, which is an alcohol, ester, carboxylic acid, or ether compound. Furthermore, the results of the FTIR test on colloidal AgNPs-As (Figure 8b) showed that the strong absorption peaks formed were 3313.94, 2118.94, and 1636.28. The peak 3313.94 belonged to an O-H bond, which is an alcohol compound with hydrogen or phenol bonds. Furthermore, the absorption peak 2118.94 belonged to a C≡C bond, which is an alkyne compound. Meanwhile, the absorption peak 1636.28 belonged to a C=C bond, which is an alkene compound.

The FTIR spectral data from previous studies show that the AgNPs were surrounded by secondary plant metabolites, such as alkaloids, terpenoids, carbonyl groups, esters, halides, and alcohol, which function as active binding sites for the AgNPs and provide stability [51, 52]. The results of the current study are supported by Daoudi *et al.* [53-55], which revealed that all peaks observed in the FTIR spectra indicate that phytomolecules, such as alcohols, aldehydes, alkanes, epoxy groups, or ether groups, are present on the surface of the resultant AgNPs, where they may be responsible for the nucleation process that converts Ag⁺ to Ag⁰.

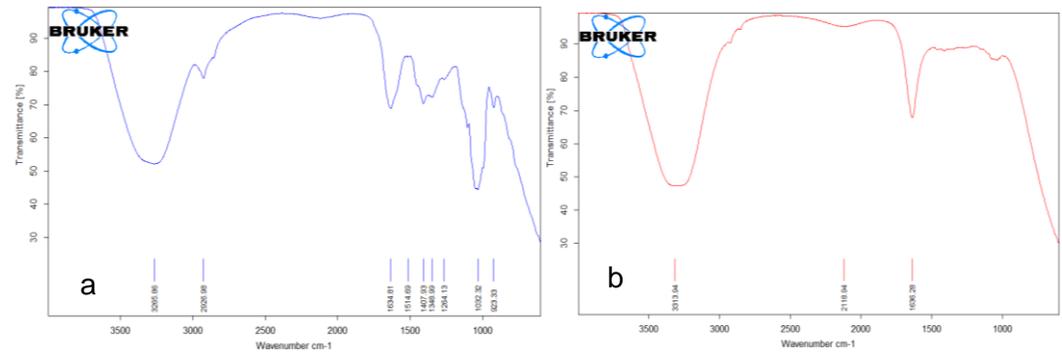


Figure 8. FTIR. a) Ethanolic single garlic extract (*Allium sativum* L.); b) AgNPs synthesized using single garlic callus extract

XRD Determination

The phase formation, crystallinity, and purity of the produced AgNPs-As were all evaluated by XRD analysis. The XRD patterns of AgNPs-As produced using single garlic callus extract are shown in Figure 9. The biosynthesis of AgNPs-As showed diffraction peaks at 21.832°, 24.136°, 28.198°, 32.617°, 46.58°, 55.128°, 57.786°, 67.729°, 74.755°, 77.013°, and 85.936°. The crystallite size of AgNPs-As was calculated to be 201.9 nm using Debye–Scherrer’s equation.

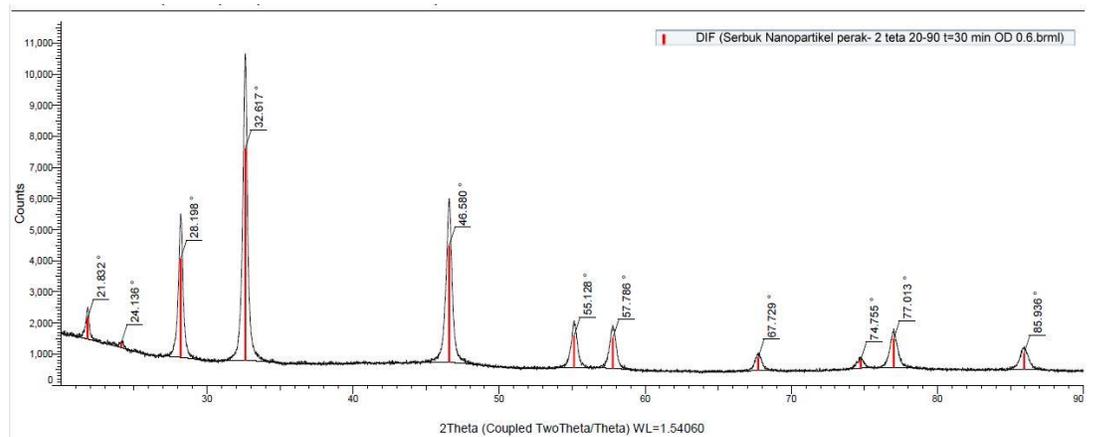


Figure 9. The XRD spectra of AgNPs synthesized using single garlic callus extract and 1 mM AgNO₃

Conclusions

During the biosynthesis of AgNPs-As from garlic callus ethanol extract, a color change indicated the formation of AgNPs-As. A wave peak at a wavelength of 400 nm is the typical optimum UV absorption spectra for AgNPs As. The AgNPs were characterized using SEM, EDX, PSA, FTIR spectroscopy, and XRD, showing that the nanoparticles had a spherical morphology, with an average size of 201.9 nm and contained several active compounds, such as alkaloids, terpenoids, carbonyl groups, esters, halides, and alcohols. These AgNPs biosynthesized using extract single garlic callus may be beneficial in the medicinal and agricultural fields. Further in vitro and in vivo research must be conducted to determine the toxicological effects.

Conflicts of Interest

The author(s) declare(s) that there is no conflict of interest regarding the publication of this paper.

Acknowledgment

This work has been supported by Department of Biology, Faculty of Mathematics and Natural Sciences, Mulawarman University, Samarinda, East Kalimantan, Indonesia.

References

- [1] Bouqellah, N. A., Mohamed, M. M., and Ibrahim, Y. (2019). Synthesis of eco-friendly silver nanoparticles using *Allium* sp. and their antimicrobial potential on selected vaginal bacteria. *Saudi Journal of Biological Sciences*, 26(7), 1789-1794.
- [2] Gupta, D. and Chauhan, P. (2017). Green synthesis of silver nanoparticles involving extract of plants of different taxonomic groups. *J Nanomed Res.*, 5(2), 00110.
- [3] Nadeem, M., Tungmunthum, D., Hano, C., Abbasi, B. H., Hashmi, S. S., Ahmad, W., and Zahir, A. (2018). The current trends in the green syntheses of titanium oxide nanoparticles and their applications. *Green Chemistry Letters and Reviews*, 11(4), 492-502.
- [4] Saputra, I. S., Suhartati, S., Yulizar, Y., and Sudirman, S. (2020). Synthesis and characterization of gold nanoparticles (AuNPs) by utilizing bioactive compound of imperata cylndrica L. *Jurnal Kimia Terapan Indonesia*, 22(1), 1-7.
- [5] Osibe, D. A., Chiejina, N. V., Ogawa, K., and Aoyagi, H. (2018). Stable antibacterial silver nanoparticles produced with seed-derived callus extract of *Catharanthus roseus*. *Artificial Cells, Nanomedicine, and Biotechnology*, 46(6), 1266-1273.
- [6] Jomini, S., Clivot, H., Bauda, P., and Pagnout, C. (2015). Impact of manufactured TiO₂ nanoparticles on planktonic and sessile bacterial communities. *Environmental Pollution.*, 202, 196-204.
- [7] Iavicoli, I., Leso, V., and Bergamaschi, A. (2012). Toxicological effects of titanium dioxide nanoparticles: a review of in vivo studies. *Journal of Nanomaterials*, 2012, 5-5.
- [8] Iavicoli, I., Leso, V., Fontana, L., and Bergamaschi, A. (2011). Toxicological effects of titanium dioxide nanoparticles: a review of in vitro mammalian studies. *Eur Rev Med Pharmacol Sci.*, 15(5), 481-508.
- [9] Gerber, A., Bundschuh, M., Klingelhofer, D., and Groneberg, D. A. (2013). Gold nanoparticles: recent aspects for human toxicology. *Journal of Occupational Medicine and Toxicology*, 8(1), 32.
- [10] Zhang, X.-D., Wu, H.-Y., Wu, D., Wang, Y.-Y., Chang, J.-H., Zhai, Z.-B., Meng, A.-M., Liu, P.-X., Zhang, L.-A., and Fan, F.-Y. (2010). Toxicologic effects of gold nanoparticles in vivo by different administration routes. *International Journal of Nanomedicine*, 5, 771-781.
- [11] Sukweenadhi, J., Setiawan, K. I., Avanti, C., Kartini, K., Rupa, E. J., and Yang, D.-C. (2021). Scale-up of green synthesis and characterization of silver nanoparticles using ethanol extract of *Plantago major* L. leaf and its antibacterial potential. *South African Journal of Chemical Engineering*, 38(1), 1-8.
- [12] Mustapha, T., Misni, N., Ithnin, N. R., Daskum, A. M., and Unyah, N. Z. (2022). A review on plants and microorganisms mediated synthesis of silver nanoparticles, role of plants metabolites and applications. *International Journal of Environmental Research and Public Health*, 19(2), 674.
- [13] Jini, D., Sharmila, S., Anitha, A., Pandian, M., and Rajapaksha, R. (2022). In vitro and in silico studies of silver nanoparticles (AgNPs) from *Allium sativum* against diabetes. *Scientific Reports*, 12(1), 22109.
- [14] Salleh, A., Naomi, R., Utami, N. D., Mohammad, A. W., Mahmoudi, E., Mustafa, N., and Fauzi, M. B. (2020). The potential of silver nanoparticles for antiviral and antibacterial applications: A mechanism of action. *Nanomaterials*, 10(8), 1566.
- [15] Padmini, R., Nallal, V. U. M., Razia, M., Sivaramakrishnan, S., Alodaini, H. A., Hatamleh, A. A., Al-Dosary, M. A., Ranganathan, V., and Chung, W. J. (2022). Cytotoxic effect of silver nanoparticles synthesized from ethanolic extract of *Allium sativum* on A549 lung cancer cell line. *Journal of King Saud University-Science*, 34(4), 102001.
- [16] Jain, A., Anitha, R., and Rajeshkumar, S. (2019). Anti inflammatory activity of Silver nanoparticles synthesised using Cumin oil. *Research Journal of Pharmacy and Technology*, 12(6), 2790-2793.
- [17] Kwak, G.-Y., Han, Y., Baik, S., Kong, B.-M., Yang, D.-C., Kang, S.-C., and Sukweenadhi, J. (2022). Gold nanoparticles green-synthesized by the *Suaeda japonica* leaf extract and screening of anti-inflammatory activities on RAW 267.4 Macrophages. *Coatings*, 12(4), 460.
- [18] Aref, M. S. and Salem, S. S. (2020). Bio-callus synthesis of silver nanoparticles, characterization, and antibacterial activities via *Cinnamomum camphora* callus culture. *Biocatalysis and Agricultural Biotechnology*, 27, 101689.
- [19] Behravan, M., Panahi, A. H., Naghizadeh, A., Ziaee, M., Mahdavi, R., and Mirzapour, A. (2019). Facile green synthesis of silver nanoparticles using *Berberis vulgaris* leaf and root aqueous extract and its antibacterial activity. *International Journal of Biological Macromolecules*, 124, 148-154.
- [20] Khan, M., Shaik, M. R., Adil, S. F., Khan, S. T., Al-Warthan, A., Siddiqui, M. R. H., Tahir, M. N., and Tremel, W. (2018). Plant extracts as green reductants for the synthesis of silver nanoparticles: Lessons from chemical synthesis. *Dalton Transactions*, 47(35), 11988-12010.
- [21] Rafique, M., Sadaf, I., Rafique, M., and Tahir, M. (2017). A review on green synthesis of silver nanoparticles and their applications. *Artificial Cells. Nanomedicine and Biotechnology*, 45(7), 1272-1291.
- [22] Jebbil, S., Fdhila, A., and Dridi, C. (2021). Nanoengineering of eco-friendly silver nanoparticles using five different plant extracts and development of cost-effective phenol nanosensor. *Scientific Reports*, 11(1), 1-11.
- [23] Roy, A., Bulut, O., Some, S., Mandal, A. K., and Yilmaz, M. D. (2019). Green synthesis of silver nanoparticles: biomolecule-nanoparticle organizations targeting antimicrobial activity. *RSC Advances*, 9(5), 2673-2702.
- [24] Nasir, S., Walters, K. F., Pereira, R. M., Waris, M., Chatha, A. A., Hayat, M., and Batool, M. (2022). Larvicidal activity of acetone extract and green synthesized silver nanoparticles from *Allium sativum* L. (Amaryllidaceae)

- against the dengue vector *Aedes aegypti* L. (Diptera: Culicidae). *Journal of Asia-Pacific Entomology*, 25(3), 101937.
- [25] Setiowati, F. K., Widoretno, W., Lukiati, B., and Prasetyawan, S. (2019). Comparison of organosulfur bioactive compounds in bulb, callus and cells suspension of single garlic (*Allium sativum* L.). *IOP Conference Series: Earth and Environmental Science*. IOP Publishing.
- [26] Prasanto, D., Riyanti, E., and Gartika, M. (2017). Uji aktivitas antioksidan ekstrak bawang putih (*Allium sativum*). *ODONTO: Dental Journal*, 4(2), 122-128.
- [27] Sutini, S., Widiwurjani, W., Purwanto, D. A., and Indrayanto, G. (2017). Teknologi kultur in vitro tanaman untuk menghasilkan metabolit sekunder & aplikasi di bidang farmasi. Research Report.
- [28] Nurchayati, Y., Santosa, S., Nugroho, L. H., and Indrianto, A. (2018). Penggunaan Kinetin, asam naftalen aasetat, dan benzil adenin dalam induksi kalus kecubung (*Datura metel* L.) secara in vitro. *Buletin Anatomi dan Fisiologi (Bulletin Anatomy and Physiology)*, 3(1), 105-109.
- [29] Iashin, I., Hasanin, M., Hassan, S. A. M., and Hashem, A. H. (2021). Green biosynthesis of zinc and selenium oxide nanoparticles using callus extract of *Ziziphus spina-christi*: characterization, antimicrobial, and antioxidant activity. *Biomass Conversion and Biorefinery*.
- [30] Solanki, A., Rathod, D., Patel, I. C., and Panigrahi, J. (2021). Impact of silver nanoparticles as antibacterial agent derived from leaf and callus of *Celastrus paniculatus* Willd. *Future Journal of Pharmaceutical Sciences*, 7(1), 1-9.
- [31] Hasanin, M., Hassan, S. A., and Hashem, A. H. (2021). Green biosynthesis of zinc and selenium oxide nanoparticles using callus extract of *Ziziphus spina-christi*: characterization, antimicrobial, and antioxidant activity. *Biomass Conversion and Biorefinery*, 1-14.
- [32] Thorpe, T. A. (2007). History of plant tissue culture. *Molecular Biotechnology*, 37(2), 169-180.
- [33] Hussain, A., Qarshi, I. A., Nazir, H., and Ullah, I. (2012). Plant tissue culture: current status and opportunities. *Recent Advances in Plant in Vitro Culture*. 6(10), 1-28.
- [34] Ochoa-Villarreal, M., Howat, S., Hong, S., Jang, M. O., Jin, Y.-W., Lee, E.-K., and Loake, G. J. (2016). Plant cell culture strategies for the production of natural products. *BMB Reports*, 49(3), 149.
- [35] Xia, Q. H., Ma, Y. J., and Wang, J. W. (2016). Biosynthesis of silver nanoparticles using *Taxus yunnanensis* callus and their antibacterial activity and cytotoxicity in human cancer cells. *Nanomaterials*, 6(9), 160.
- [36] Sari, Y. P., Kusumawati, E., Saleh, C., Kustiawan, W., and Sukartingsih, S. (2018). Effect of sucrose and plant growth regulators on callogenesis and preliminary secondary metabolic of different explant *Myrmecodia tuberosa*. *Nusantara Bioscience*, 10(3), 183-192.
- [37] Botcha, S. and Prattipati, S. D. (2019). Green synthesis of silver nanoparticles using *Hyptis suaveolens* (L.) Poit leaf extracts, their characterization and cytotoxicity evaluation against PC-3 and MDA-MB 231 cells. *Biologia*, 74, 783-793.
- [38] Khatoon, N., Mazumder, J. A., and Sardar, M. (2017). Biotechnological applications of green synthesized silver nanoparticles. *J. Nanosci. Curr. Res.*, 2(107), 2572-0813.1000107.
- [39] Usmani, A., Dash, P. P., and Mishra, A. (2018). Metallic nanoformulations: Green synthetic approach for advanced drug delivery. *Mater. Sci.*, 2(2), 1-4.
- [40] Patil, R. S., Kokate, M. R., and Kolekar, S. S. (2012). Bioinspired synthesis of highly stabilized silver nanoparticles using *Ocimum tenuiflorum* leaf extract and their antibacterial activity. *Spectrochimica Acta Part A: Molecular and Biomolecular Spectroscopy*, 91, 234-238.
- [41] Shah, M. Z., Guan, Z.-H., Din, A. U., Ali, A., Rehman, A. U., Jan, K., Faisal, S., Saud, S., Adnan, M., and Wahid, F. (2021). Synthesis of silver nanoparticles using *Plantago lanceolata* extract and assessing their antibacterial and antioxidant activities. *Scientific Reports*, 11(1), 1-14.
- [42] Vallinayagam, S., Rajendran, K., and Sekar, V. (2021). Green synthesis and characterization of silver nanoparticles using *Naringi crenulate* leaf extract: Key challenges for anticancer activities. *Journal of Molecular Structure*, 1243, 130829.
- [43] Urnukhsaikh, E., Bold, B.-E., Gunbileg, A., Sukhbaatar, N., and Mishig-Ochir, T. (2021). Antibacterial activity and characteristics of silver nanoparticles biosynthesized from *Carduus crispus*. *Scientific Reports*, 11(1), 21047.
- [44] Rajasekar, R., Samuel, M., Edison, T. N. J. I., and Raman, N. (2021). Sustainable synthesis of silver nanoparticles using *Alstonia scholaris* for enhanced catalytic degradation of methylene blue. *Journal of Molecular Structure*, 1246, 131208.
- [45] Yilmaz, D. D., Demirezen, D. A., and Mihçioğur, H. (2021). Colorimetric detection of mercury ion using chlorophyll functionalized green silver nanoparticles in aqueous medium. *Surfaces and Interfaces*, 22, 100840.
- [46] Rani, P., Trivedi, L., Gaurav, S. S., Singh, A., and Shukla, G. (2022). Green synthesis of silver nanoparticles by *Cassytha filiformis* L. extract and its characterization. *Materials Today: Proceedings*, 49, 3510-3516.
- [47] Anju, T. R., Parvathy, S., Valiya Veettil, M., Rosemary, J., Ansalna, T. H., Shahzabanu, M. M., and Devika, S. (2021). Green synthesis of silver nanoparticles from *Aloe vera* leaf extract and its antimicrobial activity. *Materials Today: Proceedings*, 43, 3956-3960.
- [48] Ahmed Naseer, M. I., Ali, S., Nazir, A., Abbas, M., and Ahmad, N. (2022). Green synthesis of silver nanoparticles using *Allium cepa* extract and their antimicrobial activity evaluation. *Chemistry International*, 8(3), 89-94.
- [49] Lade, B. D. and Shanware, A. S. (2020). Phytonanofabrication: methodology and factors affecting biosynthesis of nanoparticles, in *Smart Nanosystems for Biomedicine. Optoelectronics and Catalysis*. IntechOpen.
- [50] Peters, R., Herrera-Rivera, Z., Undas, A., van der Lee, M., Marvin, H., Bouwmeester, H., and Weigel, S. (2015). Single particle ICP-MS combined with a data evaluation tool as a routine technique for the analysis of nanoparticles in complex matrices. *Journal of Analytical Atomic Spectrometry*. 30(6), 1274-1285.
- [51] Balachandar, R., Navaneethan, R., Biruntha, M., Kumar, K. K. A., Govarthanan, M., and Karmegam, N. (2022). Antibacterial activity of silver nanoparticles phyto-synthesized from *Glochidion candolleianum* leaves.

- Materials Letters*, 311, 131572.
- [52] Widatalla, H. A., Yassin, L. F., Alrasheid, A. A., Ahmed, S. A. R., Widdatallah, M. O., Eltilib, S. H., and Mohamed, A. A. (2022). Green synthesis of silver nanoparticles using green tea leaf extract, characterization and evaluation of antimicrobial activity. *Nanoscale Advances*, 4(3), 911-915.
- [53] Daoudi, H., Bouafia, A., Meneceur, S., Laouini, S. E., Belkhalifa, H., Lebhihi, R., and Selmi, B. (2022). Secondary metabolite from nigella sativa seeds mediated synthesis of silver oxide nanoparticles for efficient antioxidant and antibacterial activity. *Journal of Inorganic and Organometallic Polymers and Materials*, 32(11), 4223-4236.
- [54] Isaac, R. R., Sakthivel, G., and Murthy, C. Research Article Green Synthesis of Gold and Silver Nanoparticles Using Averrhoa bilimbi Fruit Extract. *Journal of Nanotechnology*.
- [55] Jain, A. S., Pawar, P. S., Sarkar, A., Junnuthula, V., and Dyawanapelly, S. (2021). Bionanofactories for green synthesis of silver nanoparticles: Toward antimicrobial applications. *International Journal of Molecular Sciences*. 22(21), 11993.